

# Meltio Invar 36

Invar 36 / Alloy 36 / 1.3990

Invar is a type of nickel-iron alloy that is known for its unique properties, including low coefficient of thermal expansion and high dimensional stability over a wide range of temperatures. These characteristics make it a valuable material in various applications that require precision and stability, such as precision instruments, scientific measuring devices, cryogenics, composite molds and aerospace components.


|                     |  |
|---------------------|--|
| <b>Properties</b>   | Extremely low coefficient of thermal expansion and High Strength at low temperatures |
| <b>Applications</b> | Aerospace, Precision Components and Cryogenic Components                             |

| Wire Chemical Composition | Fe   | C    | Ni   | Mn  | Nb  | Ti  |
|---------------------------|------|------|------|-----|-----|-----|
| <b>Weight Percent [%]</b> | Bal. | 0.35 | 36.0 | 1.0 | 2.5 | 1.0 |

| Wire Density           |
|------------------------|
| 8.10 g/cm <sup>3</sup> |

| Melting Point |         |        |
|---------------|---------|--------|
| 1613 K        | 1340 °C | 2445°F |

## Spool Specs



Meltio Materials are tightly spooled and packaged to ensure the best compatibility with Meltio systems.

|                        |                      |
|------------------------|----------------------|
| <b>Wire Diameter</b>   | 1.0 mm               |
| <b>Weight on Spool</b> | 15 kg                |
| <b>Volume on Spool</b> | 1851 cm <sup>3</sup> |
| <b>Spool Type</b>      | BS300                |
| <b>Wire Coating</b>    | Uncoated             |

## Heat Treatment

Owing to the use of Invar in precision components, it is often recommended to subject it to an annealing heat-treatment after 3D printing. This is necessary as the 3D printing process introduces residual stresses, which affects the material's performance. After annealing, the sample should pass through an aging process to improve and achieve suitable mechanical properties.

### Annealing

|   |                              |
|---|------------------------------|
| Protective atmosphere<br>Heat up to 800°C | Hold for 1h<br>Cooling to RT |
|---|------------------------------|

### Aging

|   |  |
|---|--|
| Protective atmosphere<br>Heat up to 425°C | Hold at 425°C during 2h<br>Cooling in oven to RT |
|---|--|

*\*Typical Parameters for a Sample of 160x60x30 mm*

## Deposition Parameters

The following 3D printing parameters were found to provide fully dense samples. Please use the provided "Density Profiles" and refer to the document "Printing Parameters and their effect on part density" for additional information.


| Laser Power [W] | Velocity [mm/s] | Argon Flow [l/min] | Layer Height [mm] | Wire Speed [mm/s] | Energy Density [J/mm <sup>3</sup> ] |
|-----------------|-----------------|--------------------|-------------------|-------------------|-------------------------------------|
| 1100            | 7.5             | 10                 | 0.8               | 7.64              | 183                                 |

# Meltio Invar 36

Invar 36 / Alloy 36 / 1.3990

## Micrography

The as printed microstructure of Invar is heterogeneous and mostly austenite with nickel dissolving in  $\gamma$ -Fe.

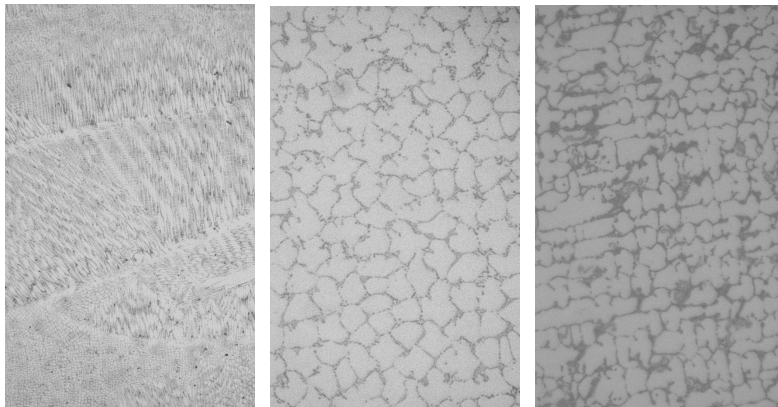


As-printed XZ  
100x Magnification

As-printed XZ  
1000x Magnification

As-printed XY  
1000x Magnification

## Tomography

Computed Tomography Scan of 3D printed sample part in Invar without detectable voids or defects. Resolution of 24  $\mu$ m per pixel.

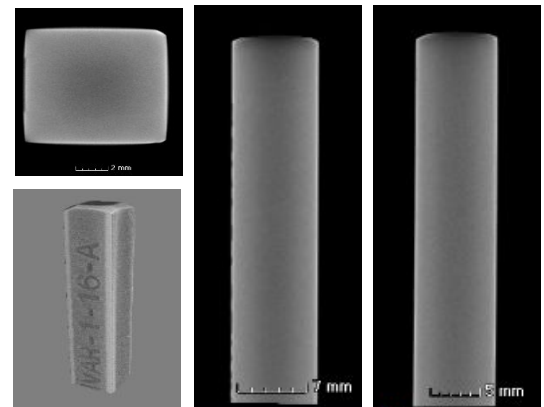

3D / Top  
View

Left View

Front View

\*Tests Carried Out In IDONIAL  
[info@idonial.com](mailto:info@idonial.com)

\*Test Carried Out In CATEC  
[info@catec.aero](mailto:info@catec.aero)

Relative density as 3D printed

99.99%

## Mechanical Properties

Results show that specimens printed using Meltio's wire-laser metal 3D printed process perform at a high level when compared to samples made with conventional manufacturing methods. Testing is carried out in the less favorable XZ Direction to ensure the values are applicable across complete part.

|   | Wrought Properties<br>(ASTM A658) | Meltio XZ Properties<br>(As Printed) |
|---|-----------------------------------|--------------------------------------|
| Ultimate Tensile strength (UTS) [MPa]   | 500                               | 522 ± 14                             |
| Yield strength [MPa]  | 241                               | 337 ± 22                             |
| Elongation [%]  | 31                                | 24 ± 2                               |
| *Tests Carried Out in CETEMET<br><a href="mailto:i+d+i@cetemet.es">i+d+i@cetemet.es</a> |                                   |                                      |
|   | Wrought Properties<br>(ASTM A658) | Meltio Properties<br>(As Printed)    |
| Hardness [HV-30]  | 127                               | 147                                  |
| *Tests Carried Out In IDONIAL<br><a href="mailto:info@idonial.com">info@idonial.com</a> |                                   |                                      |

\* Meltio's work on material characterization is carried out using the Meltio M450 and it remains under constant development. Specifications provided herein may not reflect the latest state of our research. For further information and questions please contact us via [info@meltio3d.com](mailto:info@meltio3d.com).

\*\* Any technical information or assistance provided herein is given and accepted at your own risk and neither Meltio nor its affiliates make any guarantees relating to it or because of it. Neither Meltio nor its affiliates shall be responsible for the use of this information, or any product, method or apparatus mentioned and you must make your own determination for its suitability and completeness for your application. Specifications are subject to change without notice.